EJFA Emirates Journal of Food and Agriculture

Emirates Journal of Food and Agriculture 36: 1–11
doi: 10.3897/ejfa.2024.119832

REVIEW ARTICLE

Chitosan-only nanoparticles against phytopathogenic fungi in the past decade (2013–2023)

José Rogelio Ramos-Enríquez[1], Miguel Ángel Martínez-Téllez[2], Mario Sánchez-Sánchez[2], Miguel Ángel Hernández-Oñate[3], Eber Addí Quintana-Obregón[3]

1 *Departamento de Ciencias Químico-Biológicas, Universidad de Sonora, Rosales y Luis Encinas s/n. Colonia Centro, C.P.83000, Hermosillo, Mexico*
2 *Centro de Investigación en Alimentación y Desarrollo, A.C. Coordinación de Tecnología de Alimentos de Origen Vegetal, Hermosillo, Sonora, Mexico*
3 *CONAHCYT-Centro de Investigación en Alimentación y Desarrollo, A.C. Coordinación de Tecnología de Alimentos de Origen Vegetal, Hermosillo, Sonora, Mexico*

Corresponding author: Eber Addí Quintana-Obregón (eberaddi@gmail.com)

Academic editor: Fernando Lidon ♦ **Received** 30 January 2024 ♦ **Accepted** 2 April 2024 ♦ **Published** 23 April 2024

Abstract

Chitosan is a biocompatible, biodegradable, and antimicrobial polymer. Researchers have recently explored using chitosan nanoparticles to fight phytopathogenic fungi. This review aims to provide a comprehensive overview of studies conducted between 2013 and 2023 using the most popular databases for academic research on this topic. A systematic review was conducted using Software Rayyan to support the process. The search was conducted using the Web of Science, Scopus, and ScienceDirect databases. Out of the 752 records found from 2013–2023, only 83 articles were considered eligible for inclusion in the review after screening with inclusion and exclusion criteria. Most studies showed that chitosan nanoparticles are produced using sodium tripolyphosphate (TPP) through ionotropic gelation. However, using TPP has potential drawbacks and may have a synergistic effect with chitosan, which requires further investigation. TPP can affect the biological activity of the nanoparticle matrix. Furthermore, less than 10 out of the 83 articles reviewed in the time frame explored chitosan-only nanoparticles (nanochitosan) against phytopathogenic fungi. This shows the need for more research to determine the potential benefits of chitosan-only nanoparticles in control phytopathogenic fungi.

Keywords

Antifungal, Nanochitosan, Nanoparticles, Sodium tripolyphosphate

Introduction

The biocompatibility, biodegradability, and antimicrobial activity of chitosan have led to its evaluation in various formulations for use in agriculture, food production, and crop protection against pathogens. For the year 2023, 9,767 papers were retrieved from the Web of Science Core Collection using your search engine, showing the extensive body of research attesting to the many advantages of these polymers across several domains (Table 1). Nanotechnology is a relatively new scientific field (Haris et al. 2023) that focuses on reducing the particle size of materials to the nanoscale of 1–100 nm while also enhancing their biological activity (Ansari 2023; Malik et al. 2023). It is essential to note that in polymeric systems, the definition of nanoparticle generally extends up to 1000 nm size (Jonassen et al. 2012; Zielińska et al. 2020; Lang et al. 2021). Current scholarly progress includes the development of novel agricultural goods that shield plants from pathogens (Ansari 2023), as well as the creation of complex nanoparticles based on chitosan and nanochitosan (chitosan-only nanoparticles) because the nanoscale increases inhibition against fungi pathogens

Copyright *Ramos-Enríquez, et al.* This is an open access article distributed under the terms of the Creative Commons Attribution License (CC-BY 4.0), which permits unrestricted use, distribution, and reproduction in any medium, provided the original author and source are credited.

(Kheiri et al. 2016; El-Mohamedy et al. 2019). However, there is knowledge to be generated; for example, when changing the search for chitosan to nanochitosan and chitosan nanoparticles, 246 articles were found during the past decade (only 24 in 2023) according to the Web of Science search engine. Based on the 17 goals of the United Nations' Sustainable Development 2030 Agenda, the number of agriculture-related articles was reduced (see Table 2). There is a significant potential to assess the benefits and drawbacks of applying nanochitosan in crop protection. This literature analysis aimed to provide a comprehensive overview of studies conducted between 2013 and 2023 to assess the existing understanding of nanochitosan in phytopathogenic fungi, particularly to find research on nanoparticles composed exclusively of chitosan.

Table 1. Results from the Web Science search engine with entry information on chitosan with filter year 2023.

Document Type	Record Count	% of 9,767
Article	8,449	86.51
Review Article	1,210	12.39
Early Access	1,070	10.95
Correction	43	0.44
Meeting Abstract	32	0.33
Book Chapters	12	0.12
Proceeding Paper	12	0.12
Editorial Material	10	0.10
Letter	8	0.08
Retraction	6	0.06
Expression Of Concern	1	0.01

Data from the Web of Science. The search was performed at 9:45 AM (Pacific Time) on 12/14/2023.

Methods

To be considered for inclusion in this review, papers had to have been retrieved from the databases ScienceDirect, Web of Science, and Scopus. A search approach combines the keywords "chitosan nanoparticles", "nanochitosan", "fungi", and "fungal". The Boolean operators "OR" and "AND" were used for a more precise search with the following nomenclature: [chitosan nanoparticles OR nanochitosan] AND [fungi OR fungal]. Then, the results were filtered. First, the duplicate articles were removed. Later, records were excluded based on specific selection criteria with information in the titles and abstract. The criteria for inclusion were: (1) only research papers; reviews and chapters were excluded; (2) Articles had to have been published between 2013 and 2023; (3) Articles had to be written in the English language. Also, exclusion criteria encompassed research or models devoid of fungus and studies including yeast. The management of articles was supported by Software Rayyan (Free Plan) (Ouzzani et al. 2016). Other references were included to supply further explanations or to present varying viewpoints on particular subjects.

Table 2. Results of articles related to some Sustainable Development Goals and closely linked to agriculture from the Web Science search engine using the keywords nanochitosan and chitosan nanoparticles (2013–2023).

Sustainable Development Goals	Record Count	% of 246	closely linked to agriculture
03 Good Health and Well Being	78	31.71	
06 Clean Water and Sanitation	48	19.51	
11 Sustainable Cities and Communities	41	16.67	
14 Life Below Water	7	2.85	
02 Zero Hunger	5	2.03	✓
13 Climate Action	2	0.81	
12 Responsible Consumption and Production	1	0.41	✓
15 Life on Land	1	0.4 1	✓

Data from the Web of Science. The search was performed at 9:40 AM (Pacific Time) from 12/14/2023.

Results and discussion

Fig. 1 illustrates the number of papers that evaluated the efficacy of chitosan nanoparticles against phytopathogenic fungi. These publications were disseminated through

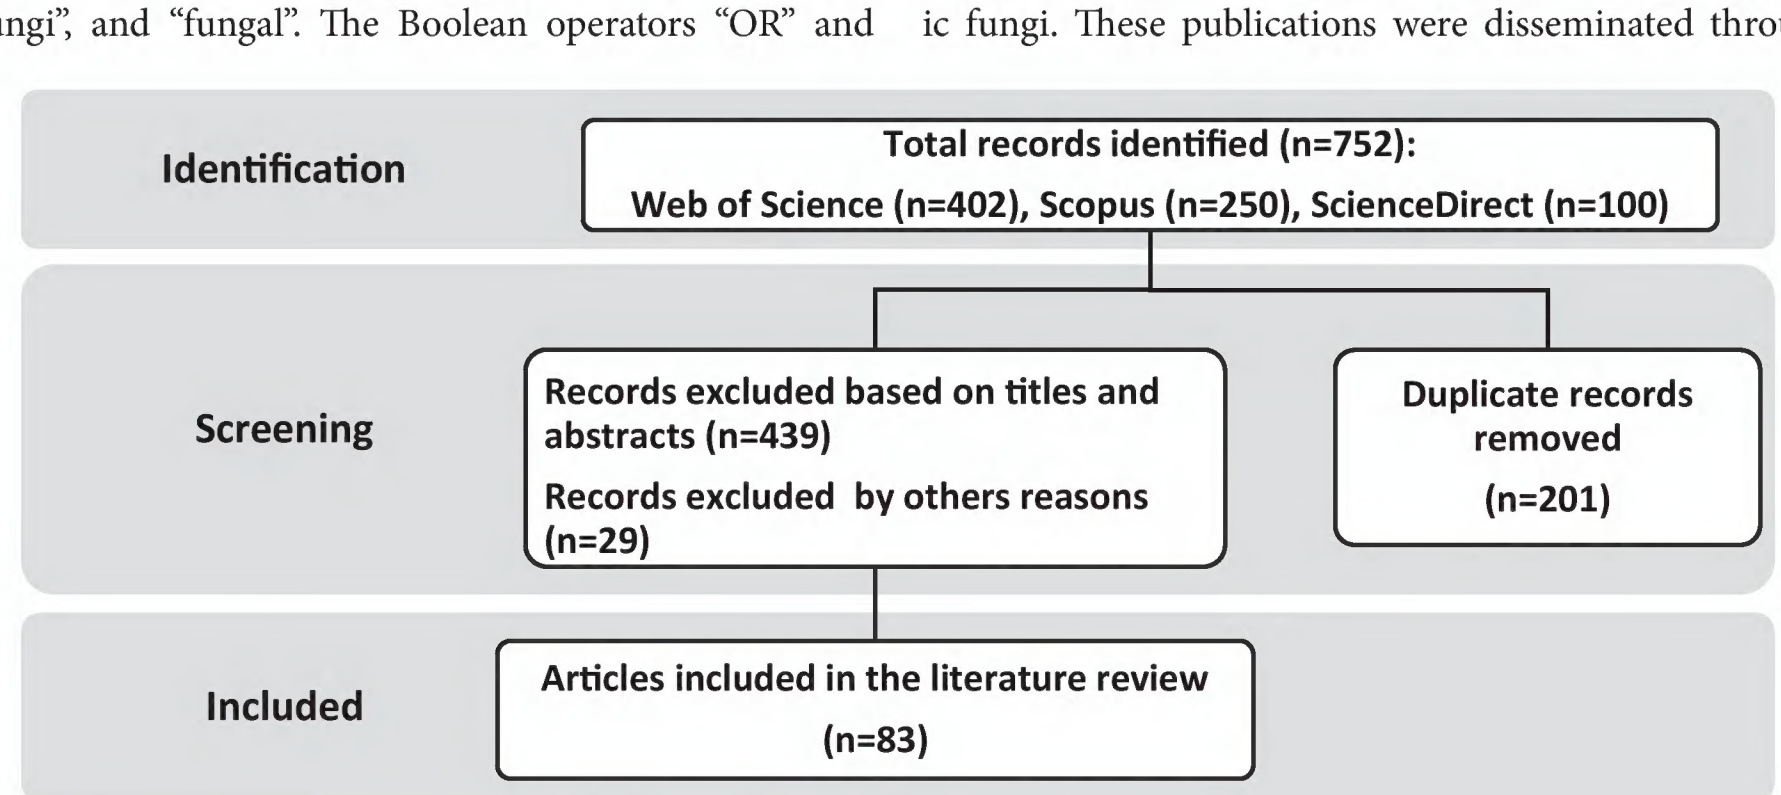

Figure 1. Flow diagram with results of articles used in the review.

the Web of Science, Scopus, and ScienceDirect databases from 2013 to 2023. Of the 83 studies reviewed, 47 (56%) used sodium tripolyphosphate (TPP) to create chitosan nanoparticles. The ionotropic gelation method (IG) was the most used. The resulting particle sizes were mainly less than 400 nm, as reported in Tables 3, 4. Additionally, 29 out of the 47 studies (more than 50%) that used TPP examined the nanoparticles for potential use as carriers of other molecules or substances to enhance the effectiveness of chitosan.

Compounds such as metals, fungicides, essential oils, and vegetable extracts (mostly alcoholic) are examples of molecules or substances for carriers or mixed with chitosan-TPP (Table 4). The most described method for preparing chitosan nanoparticles in the literature is the TPP method, which is simple and easy to use (Bugnicourt and Ladavière 2016). This review shows that this tendency persisted until 2023. Sometimes, the word TPP is left out from the title or abstract of certain articles. This can give the impression that the discussed nanoparticles are made solely of chitosan. However, upon closer examination of the method used to create the nanoparticles, it becomes clear that IG or some other method involving TPP is used.

Chitosan-TPP and nanochitosan

The omission of TPP in the titles and abstracts maybe because it is the most used compound for producing chitosan nanoparticles and is considered safe. However, Hsissou et al. (2021) describe a composite material as "*the assembly of two or more materials, the final assembly having properties superior to the properties of each of the constituent materials*." Also, Zweben (2024) defines composite as "*two or more materials bonded together, have revolutionary properties compared to traditional monolithic materials*," and Fakirov (2015) explains, "*Polymer–polymer composites are then such composites whose reinforcement and matrix belong to two chemically different materials*." To distinguish it from nanoparticles made from chitosan alone, it is important to name the matrix chitosan-TPP as a nanocomposite rather than nanochitosan. The word nanochitosan should be used for particles made with chitosan-only. Although chitosan is the primary component in chitosan-TPP, and it could be argued that its biological activity is solely due to chitosan, it is still possible that there is a synergistic effect between chitosan and TPP. Koukaras et al. (2012) have reported that chitosan-TPP contains mostly chitosan, but it is essential to recognize the potential contribution of TPP to the overall biological activity of the nanocomposite.

TPP synergistic effect

Sodium tripolyphosphate ($Na_5P_3O_{10}$) (TPP) is a crystalline inorganic salt anionic that belongs to the group of condensed phosphates and is used mainly for the industry of detergents (Makara et al. 2016). Also, it is widely used in the IG method to cross-link polycationic polymers, and the elaboration of chitosan nanoparticles is not the exception for being considered physiologically non-toxic (Rampino et al. 2013; Dmour and Taha 2018). The nanoparticles of chitosan-TPP are a consequence of the ionic interaction between amino groups ($-NH^{+}{}^{3}$) of chitosan and phosphate groups of TPP ($-P_3O^{-5}{}_{10}$) and particle formed contend phosphorus in the structure (Antoniou et al. 2015; Sarkar et al. 2022). It is possible that some authors do not use TPP controls due to its low content compared to chitosan and the limited activity of TPP because of ionic interactions with chitosan (Rampino et al. 2013).

Mondéjar-López et al. (2022) show that chitosan-TPP nanoparticles do not impede the germination of wheat, barley, and oats seeds, and the potential exists for chitosan-TPP-fungicide nanoparticles to mitigate the phytotoxic impact of pure fungicides on plants, although in certain circumstances (Maluin et al. 2020). On the contrary, the study conducted by Asgari-Targhi et al. (2018) reveals that the growth and development of *Capsicum annuum* were significantly inhibited by chitosan-TPP nanoparticles (5, 10, and 20 mg L^{-1}). Wang et al. (2021) found that the impact of TPP varied, with positive or negative effects contingent upon the plant organ; specifically, the authors reported that TPP promoted leaf development while impeding stem growth. On the other hand, Chouhan et al. (2022) report that kidney cells were altered from a concentration of 0.3 mg/mL chitosan-TPP nanoparticles to give a negative response and cause reproductive inability. Divya et al. (2018) reported on the cytotoxicity activity of fibroblast cells. They measured the percentage of viable cells and percent cytotoxicity. After 24 hours of incubation, 300 mg/mL killed 74.16% of the cells, obtaining an LD_{50} value of 64.21 mg/mL. Moreover, few researchers, such as Xiong et al. (2023) and Cota-Arriola et al. (2013), have evaluated or discussed this possible synergistic biological activity between chitosan and TPP. Earlier reports have shown that TPP has antifungal activity against fungi phytopathogens (Knabel et al. 1991; Cota-Arriola et al. 2013; Jakovljevic et al. 2014). These reports suggest that the effects of chitosan-TPP nanoparticles could be governed by a synergistic, which can have a positive or negative impact depending on the interacting organism of the nanoparticle. Further studies are needed to determine the full range of potential disadvantages of chitosan-TPP nanoparticles against fungal phytopathogens.

The effects of the TPP component after the breakdown of chitosan-TPP nanoparticles are unclear. This review cannot answer concerns about residual TPP accumulation and its potential impact on non-target organisms. Previously, Palmeira-de-Oliveira et al. (2011) reported that the overall *in vitro* activity of TPP has not been investigated. However, several studies have shown that the environmental problem known as eutrophication and changes in proteases and protein fungal activity can be generated with the used TPP (Stojanović et al. 2010; Stojanović et al. 2011; Jakovljević et al. 2020). To avoid these negative effects, it is recommended to seek alter-

Table 3. List of research studies conducted between 2013 and 2023 that evaluated the efficacy of Chitosan-TPP nanoparticles against phytopathogenic fungi.

#	Reference	Fungal	Crop	Characteristic nanoparticle		Major findings for this review
				Size (nm)	Potential Z (mV)	
1	El-Mohamedy et al. (2019)	*Alternaria solani* *Botryties cinerea* *Fusarium oxysporium* *Fusarium sembaticum* *Fusarium solani* *Macrophomina phaseolin* *Phytophthora infestance* *Rhizoctonia solani* *Sclerotina. Sclerotiorum* *Sclerotium rolfsii*	Tomato Potato Green bean	40–70	48	Concentrations 0.1% and 0.05% showed completely inhibited (100%) the mycelial growth of all tested pathogens
2	Sarkar et al. (2022)	*Alternaria alternata*	*Capsicum annuum L.*	<100	---	100% inhibition to 0.1%
3	Izadi et al. (2021)		Tomato	150	32	Antifungal activity
4	Sen et al. (2022)	*Aspergillus flavus*	Mung bean [*Vigna radiata* (L.) R. Wilczek]	~260	100	Inhibition spore germination
5	Singh et al. (2020a)		---	40–100	41	Low effects antifungal
6	Elshaer et al. (2022)	*Aspergillus niger*	---	216–263	----	MIC:256.0 µg/mL MFC: 512.0 µg/mL
7	Hasheminejad et al. (2019)		---	129.83	31	Inhibition up 50% to 187 µg/mL
8	Melo et al. (2020)	 *Botrytis cinerea* *Rhizopus stolonifer*	Strawberry	331	34	Inhibition <50% in fruit infected Inhibition >60% in fruit infected Inhibition <50% in fruit infected
9	López-Meneses et al. (2018)	*Aspergillus parasiticus*	Corn grain	361.9	43.8	Lower inhibition
10	Mondéjar-López et al. (2022)	*Aspergillus niger* *Aspergillus versicolor* *Fusarium oxysporum*	Wheat Oat Barley	172	49.8	MIC: 1.11 µg/mL MIC: >3.33 µg/mL MIC: 3.33 µg/mL On spore germinated
11	Abdel-Aliem et al. (2019)	*Aspergillus niger* *Aspergillus terreus* *Baeuvaria bassiana* *Fusarium oxysporum* *Fusarium graminearum*	Nut	180	---	Mycelium Inhibition >60% 800 ppm inhibits Zearalenone production
12	Alotaibi et al. (2019)	*Aspergillus flavus* *Aspergillus ochraceus* *Fusarium moniliforme*	*Phoenix dactylifera*	35–65	---	Inhibition of growth fungi evaluated
13	Hesami et al. (2021)	*Botrytis cinerea*	Strawberries	187	39	lowest inhibition against fruit decay to 20/µg mL
14	Mohammadi et al. (2015)			96.93	53	1500 ppm for inhibition up 50%
15	OH et al. (2019)	*Colletotrichum gelosporidies*, *Phytophthora capsica* *Sclerotinia sclerotiorum* *Fusarium oxysporum* *Gibberella fujikuori*	Tomato	~100–1000	---	Antifungal activity
16	Divya et al. (2018) Divya et al. (2017)	 *Fusarium oxysporum* *Rhizoctonia solani* *Colletotrichum acutatum* *Phytophthora infestans*	Tomato Chilly Brinjal	20–70	---	Inhibited Mycelial radial growth: 63.88% at 40 mg/mL 84.72% at 50 mg/mL 76.72% at 50 mg/mL 32.16% at 50 mg/mL
17	El-Morsy et al. (2023)	*Fusarium equiseti*	Tomato	60	90.7	Inhibition rate for isolates: 40.39–66.0%
18	Kheiri et al. (2016)	*Fusarium graminearum*	Wheat	180.9	45.6	85% inhibition to 5000 ppm
19	Kheiri et al. (2017)					
20	Karamchandani et al. (2022)	 *Fusarium moniliforme*	----	256 144	24.5 46.5	 0.20% for inhibition fungal growth, up 80%
21	Muzzalupo et al. (2020)	*Fusarium proliferatum*	*Allium sativa*	260	25	Fungal inhibition up to 48.71%

#	Reference	Fungal	Crop	Characteristic nanoparticle		Major findings for this review
				Size (nm)	Potential Z (mV)	
22	Chouhan et al. (2022)	*Fusarium solani*	Wheat	21–124	---	65.50% of radial growth inhibition and 89% inhibition of spore germination to 40 µg/mL
23	Dananjaya et al. (2017)	*Fusarium oxysporum*	---	275	36	MIC: 400 µg/mL
24	Boruah and Dutta (2021)	*Sclerotium rolfsii* *Rhizoctonia solani*	---	310–342	-15.36	Chitosan from fungal chitin Maximum Radial growth inhibition: *Fusarium oxysporum*, 60.14% *Sclerotium rolfsii*, 45.03% *Rhizoctonia solani*, 63.2%
25	Hoang et al. (2022)	*Lasiodiplodia pseudotheobromae* *Alternaria alternate* *Penicillium digitatum*	Citrus	50–250	98.7	200 ppm exhibited the highest activity in totally inhibiting
26	Salem et al. (2022)	*Penicillium digitatum*	Citrus fruit	22.18–159.73	38.8	MFC for isolates 32.5–35 mg/mL
27	Xing et al. (2021)	*Penicillium steckii* *Aspergillus oryzae*	---	---	---	MIC: 5 mg/mL MFC: >5 mg/mL MIC: >5 mg/mL MFC: >5 mg/mL
28	Manikandan and Sathiyabama (2016)	*Pyricularia grisea*	Rice	83.32	-28	Not show direct inhibitory activity against fungi
29	Pham et al. (2019)	*Pyricularia oryzae*	Rice	25–30	-3	Lowest antifungal activity
30	Divya et al. (2020)	*Rhizoctonia solani*	*Oryza sativa L*	---	---	1000 µg/mL uppress 90% disease in detached leaf assay

---: not applicable or not reported. MFC: Minimal fungicide concentration MIC: Minimal inhibitory concentration.

Table 4. List of research studies (from 2013 to 2023) that evaluate Chitosan-TPP nanoparticles as carriers or composites of other molecules or substances against phytopathogenic fungi.

#	Reference	Fungal	Crop	Molecules or substances added to matrix nanoparticles	Characteristic nanoparticle		Major findings for this review
					Size (nm)	Potential Z (mV)	
1	Izadi et al. (2021)	*Alternaria alternata*	Tomato	*Carum copticum* EO	190.6	+29.4	Antifungal activity
2	Saharan et al. (2013)		---	Copper	180–487	+88	High inhibition fungi
		Macrophomina phaseolina *Rhizoctonia solani*		Saponins	200–990	+31	
3	Saharan et al. (2015)	*Alternaria Solani* *Fusarium oxysporum*	Tomato	Copper	374.3	+22.6 mV	0.12% caused 70.5 and 73.5% inhibition of mycelia growth and 61.5 and 83.0% inhibition of spore germination in *Alternaria solani* and *Fusarium oxysporum*, respectively.
4	Karami-Osboo et al. (2023)	*Aspergillus flavus*	Pistachio nut	*Zataria multiflora* (Boiss) EO	293 ± 17	+16.8	inhibiting aflatoxin B1 production
5	Mumtaz et al. (2022)		----	Voriconazole	NA	NA	Antifungal activity
6	Singh et al. (2020a)		---	*Bunium persicum* (Boiss) EO	80–300	+33.8	Inhibition of 100% growth and aflatoxin B1 production to 0.8 µg/ml
7	Tiwari et al. (2022)		---	*Cinnamomum glaucescens* EO	45.8–104.8	---	MIC = 0.9 µL/mL aflatoxin inhibition to 0.8 µL/mL
8	Dwivedy et al. (2018)		*Pistacia vera*	*Illicium verum* EO	<200	---	Inhibiting aflatoxin B1 at 0.2 µL/mL
9	Das et al. (2021)		----	*Pimpinella anisum* EO	21–38	---	MIC: 0.08 µL/mL and inhibition antiaflaxotinB1
		Curvularia lunata *Alternaria humicola* *Alternaria alternata*					Nanoencapsulation preserved the antifungal properties for a longer time
10	Elshaer et al. (2022)	*Aspergillus niger*	---	Thompson Seedless	59–124	---	MIC:128 µg/mL MFC: 256 µg/mL
				Vitis vinifera juice extract Clotrimazole	67–75	---	MIC:32 µg/mL MFC: 64 µg/mL
				Thompson Seedless *Vitis vinifera* juice extract/Clotrimazole	50–89	+31	MIC:2 µg/mL MFC: 2 µg/mL

#	Reference	Fungal	Crop	Molecules or substances added to matrix nanoparticles	Characteristic nanoparticle		Major findings for this review
					Size (nm)	Potential Z (mV)	
11	Hasheminejad et al. (2019)		---	Clove EO	268	+22	Inhibition mycelial
12	El-Aziz et al. (2018)	*Aspergillus niger*	---	Mentha longifolia extract	157	≈+36	Antifungal activity
13	Mondéjar-López et al. (2022)	*Aspergillus versicolor* *Fusarium oxysporum*	Wheat Oat Barley	Garlic EO	172–352	+19–32	MIC: 0.37 µg/mL MIC: 3.33 µg/mL MIC: 1.11 µg/mL On spore germination
14	Nasiri-Jahrodi et al. (2022)	*Aspergillus fumigatus*	---	Eugenol	300–330	---	MIC: 300 µg/mL MFC: 600 µg/mL increase the expression of CYP51 gen
15	López-Meneses et al. (2018)	*Aspergillus parasiticus*	Corn grain	*Schinus molle L.* EO	516.9	+40.2	500 µg/mL inhibited up to 59% the aflatoxin production
16	Mohammadi et al. (2015)	*Botrytis cinerea*	Strawberry	*Zataria multiflora EO*	124.67–174.03	+46.6–67.8	750 ppm for inhibition 100%
17	Youssef et at. (2019)		Table grapes	Silica	48	---	100% inhibition to 10000 µg/mL
18	Hesami et al. (2021)		Strawberry	*Pistacia atlantica* EO	215.3–632.5	+10.46–34.11	Hight inhibition against fruit decay to 20 µg/mL
19	Wu et al. (2023)	*Colletotrichum gloeosporioides*	Strawberry	O-carboxymethyl chitosan/ tebuconazole	NA	NA	Antifungal activity
20	Chouhan et al. (2022)	*Fusarium solani*	Wheat	Niquel	300–400		100% of inhibition on spore germination and radial growth to 40 µg/mL
21	Dananjaya et al. (2017)	*Fusarium oxysporum*	---	Silver	373 ± 28	+47.5	MIC: 100 µg/mL
22	Kumar et al. (2022a)	*Fusarium pallidoroseum*	---	Mancozeb	292.4–443.9	+14.8–17.8	Antifungal activity
23	Muzzalupo et al. (2020)	*Fusarium proliferatum*	*Allium sativa*	*In vitro* Olive Leaf Extracts	254.6	16.9	Inhibition fungal up to 67.41%
24	Salem et al. (2022)	*Penicillium digitatum*	Citrus fruit	*Punica granatum* peel extract- selenite	24.58–164.71	+ 31.7	MFC for isolates 22.5–27.5 mg/mL
25	Pham et al. (2019)	*Pyricularia oryzae*	Rice	Protocatechuic acid	30–35	+11	Stronger anti-fungal properties at 5000 ppm
26	Sathiyabama and Muthukumar (2020)	*Pyricularia grisea*	Rice	*guar gum*	NA	NA	Activity against blight disease of rice
27	Jose et al. (2022)	*Pythium aphanidermatum*	---	clove oil	NA	NA	Antifungal activity
28	Sathiyabama et al. (2022)	*Rhizoctonia bataticola*	Chickpea	Thiamine	NA	NA	Antifungal activity
29	Mazzotta et al. (2022)	*Verticillium dahliae*	Tomato	Olive leaves extracts	331.26	21.1	MIC: 0.14 mg/mL

---: not applicable or not reported. NA: Full text is unavailable, only by subscription or buy article. EO: Essential oil. MFC: Minimal concentration fungicide.

natives to TPP that do not introduce compounds to the chitosan polymer matrix. Alternatively, safe compounds whose effects on the environment and non-target biological systems have been fully tested can be used. More research is required to determine the biological activity of chitosan-TPP and TPP.

Chitosan-only nanoparticles (nanochitosan)

This review exclusively focuses on nanoparticles made up of chitosan, but only twenty-six articles have studied nanoparticles without reporting the use of TPP in a composite matrix. The compounds mixed with chitosan are copper (Hassan et al. 2022; Dorjee et al. 2023), gold (Lipșa et al. 2020; Lipșa et al. 2021), nickel (Parthasarathy et al. 2023), silver (Matei et al. 2018; Gordienko et al. 2019), zinc (Alharbi et al. 2022), pinene (Hernández-López et al. 2020), proteins (Sathiyabama and Parthasarathy 2016; Hernández-Téllez et al. 2017), sodium sulfate (in place of TPP; Hashim et al. 2019), propolis (Cortés-Higareda et al. 2019), oil (Wardana et al. 2023), essentials oils (Luque-Alcaraz et al. 2016; Chávez-Magdaleno et al. 2018; Kalagatur et al. 2018; Yadav et al. 2019; Yilmaz et al. 2019; Kumar et al. 2020, 2022b; Singh et al. 2020b; Das et al. 2022), and vegetable extracts (Ali et al. 2022; El-Naggar et al. 2022; Istúriz-Zapata et al. 2022).

Only a few articles in this research have evaluated nanochitosan, which refers to nanoparticles made of chitosan-only. Some of these studies used nanochitosan as a control to compare the particle size of mixtures of chitosan and other compounds without evaluating the antifungal activity of nanochitosan itself (Kumar et al. 2019;

Singh et al. 2020b). Abdelraouf et al. (2023) used nanochitosan with a size range of 80–100 nm as a control in their experiment. They found that reduced the percentage of *Fusarium* wilt infection in tomato plants without affecting the growth of plants. In addition, Abdel-Rahman et al. (2021) reported that nanochitosan with a size of less than 100 nm and at concentrations of 0.2 and 0.4 g/L, inhibited the growth of *Penicillium expansum*, which is a pathogen that affects apples. Istúriz-Zapata et al. (2022) found that using nanochitosan (5 nm) up to a dosage of 100 µL/mL resulted in no growth of fungi *in vitro*, including *Colletotrichum asianum*, *Fusarium solani*, *Lasiodiplodia theobromae*, *Neofusicoccum oculatum*, *Pestalotiopsis mangiferae*, and *Talaromyces variabilis*. Chávez-Magdaleno et al. (2018) reported that nanochitosan had preventive activity against *Colletotrichum gloeosporioides* in avocados, while Wardana et al. (2023) discovered that (43.77–70.61 nm) exhibited antifungal activity against *Rhizopus stolonifer*. Moreover, in a study conducted by Cortés-Higareda et al. (2019), it was found that nanochitosan (3 nm) showed a minor inhibition of up to 25% on spore germination and mycelial growth in some fungi such as *Aspergillus flavus*. On the other hand, some reports have shown less or non-activity of nanochitosan against fungal pathogens. Luque-Alcaraz et al. (2016) discovered that nanochitosan (20–100 nm) did not significantly reduce the number of viable spores of *Aspergillus parasiticus in vitro*. This data suggests that the fungi may be lowly susceptible to nanochitosan. The above-described highlights the need to conduct more research to fully understand the benefits of nanochitosan in the combat against phytopathogenic fungi. Although nanoparticles have great potential to improve human life, handling and managing them correctly is important to prevent any negative effects on biological systems, including nanotoxicology.

Conclusions

This review delved into the characteristics of chitosan nanoparticles, both with and without TPP. However, only a limited number of studies investigated chitosan-only nanoparticles. Thus, there is a critical need for further research on nanochitosan to ensure their safe and effective use in biological systems, highlighting the significance of proper handling and precautionary measures.

Funding

This research and article processing charge (APC) were funded by Consejo Nacional de Humanidades Ciencia y Tecnología (FOSEC-SEP-INVESTIGACIÓN BÁSICA; FSSEP02-C-2018-2), grant number A1-S-34064 - "Respuestas transcripómicas de complejos de *Colletotrichum* expuestos a nanopartículas de quitosano en un modelo *in vitro*".

Competing interests

The author has declared that no competing interests exist.

References

Abdel-Aliem HA, Gibriel AY, Rasmy NM, Sahab AF, El-Nekeety AA, Abdel-Wahhab MA (2019) Antifungal efficacy of chitosan nanoparticles against phytopathogenic fungi and inhibition of zearalenone production by *Fusarium graminearum*. Comunicata Scientiae 10(3): 338–345. https://doi.org/10.14295/cs.v10i3.1899

Abdelraouf AMN, Hussain AA, Naguib DM (2023) Nano-chitosan encapsulated *Pseudomonas fluorescens* greatly reduces *Fusarium* wilt infection in tomato. Rhizosphere 25: 100676. https://doi.org/10.1016/j.rhisph.2023.100676

Abdel-Rahman FA, Monir GA, Hassan MS, Ahmed Y, Refaat M.H, Ismail IA, El-Garhy HA (2021) Exogenously applied chitosan and chitosan nanoparticles improved apple fruit resistance to blue mold, upregulated defense-related genes expression, and maintained fruit quality. Horticulturae 7(8): 224. https://doi.org/10.3390/horticulturae7080224

Alharbi ND, Amer HH, El-Zaher NA, Guirguis OW (2022) Development and characterization of cotton fabrics by dipping in solutions of chitosan and ZnO-nanoparticles as promising environmentally friendly reinforcements for polymer composites. Polymers and Polymer Composites 30. https://doi.org/10.1177/09673911221148826

Ali LM, Ahmed AERAER, Hasan HES, Suliman AERE, Saleh SS (2022) Quality characteristics of strawberry fruit following a combined treatment of laser sterilization and guava leaf-based chitosan nanoparticle coating. Chemical and Biological Technologies in Agriculture 9(1): 1–13. https://doi.org/10.1186/s40538-022-00343-x

Alotaibi MA, Tayel AA, Zidan NS, El Rabey HA (2019) Bioactive coatings from nano-biopolymers/plant extract composites for complete protection from mycotoxigenic fungi in dates. Journal of the Science of Food and Agriculture 99(9): 4338–4343. https://doi.org/10.1002/jsfa.9667

Ansari MA (2023) Nanotechnology in food and plant science: challenges and future prospects. Plants 12(13): 2565. https://doi.org/10.3390/plants12132565

Antoniou J, Liu F, Majeed H, Qi J, Yokoyama W, Zhong F (2015) Physicochemical and morphological properties of size-controlled chitosan–tripolyphosphate nanoparticles. Colloids and Surfaces A: Physicochemical and Engineering Aspects 465: 137–146. https://doi.org/10.1016/j.colsurfa.2014.10.040

Asgari-Targhi G, Iranbakhsh A, Ardebili ZO (2018) Potential benefits and phytotoxicity of bulk and nano-chitosan on the growth, morphogenesis, physiology, and micropropagation of *Capsicum annuum*. Plant Physiology and Biochemistry 127: 393–402 https://doi.org/10.1016/j.plaphy.2018.04.013

Boruah S, Dutta P (2021) Fungus mediated biogenic synthesis and characterization of chitosan nanoparticles and its combine effect with *Trichoderma asperellum* against *Fusarium oxysporum*, *Sclerotium*

rolfsii and *Rhizoctonia solani*. Indian Phytopathology 74(1): 81–93. https://doi.org/10.1007/s42360-020-00289-w

Bugnicourt L, Ladavière C (2016) Interests of chitosan nanoparticles ionically cross-linked with tripolyphosphate for biomedical applications. Progress in Polymer Science 60: 1–17. https://doi.org/10.1016/j.progpolymsci.2016.06.002

Chávez-Magdaleno ME, Luque-Alcaraz AG, Gutiérrez-Martínez P, Cortez-Rocha MO, Burgos-Hernández A, Lizardi-Mendoza J, Plascencia-Jatomea M (2018) Effect of chitosan-pepper tree (*Schinus molle*) essential oil biocomposites on the growth kinetics, viability and membrane integrity of *Colletotrichum gloeosporioides*. Revista Mexicana de Ingeniería Química 17(1): 29–45. https://doi.org/10.24275/uam/izt/dcbi/revmexingquim/2018v17n1/Chavez

Chouhan D, Dutta A, Kumar A, Mandal P, Choudhuri C (2022) Application of nickel chitosan nanoconjugate as an antifungal agent for combating Fusarium rot of wheat. Scientific Reports 12(1): 14518. https://doi.org/10.1038/s41598-022-18670-2

Cortés-Higareda M, Ramos-García ML, Correa-Pacheco ZN, del Río-García JC, Bautista-Baños S (2019) Nanostructured chitosan/propolis formulations: characterization and effect on the growth of *Aspergillus flavus* and production of aflatoxins. Heliyon 5(5): e01776. https://doi.org/10.1016/j.heliyon.2019.e01776

Cota-Arriola O, Cortez-Rocha MO, Ezquerra-Brauer JM, Lizardi-Mendoza J, Burgos-Hernández A, Robles-Sánchez RM, Plascencia-Jatomea M (2013) Ultrastructural, morphological, and antifungal properties of micro and nanoparticles of chitosan crosslinked with sodium tripolyphosphate. Journal of Polymers and the Environment 21: 971–980. https://doi.org/10.1007/s10924-013-0583-1

Dananjaya SHS, Erandani WKCU, Kim CH, Nikapitiya C, Lee J, de Zoysa M (2017) Comparative study on antifungal activities of chitosan nanoparticles and chitosan silver nano composites against *Fusarium oxysporum* species complex. International Journal of Biological Macromolecules 105: 478–488. https://doi.org/10.1016/j.ijbiomac.2017.07.056

Das S, Singh VK, Chaudhari AK, Dwivedy AK, Dubey NK (2022) Co-encapsulation of *Pimpinella anisum* and *Coriandrum sativum* essential oils based synergistic formulation through binary mixture: Physico-chemical characterization, appraisal of antifungal mechanism of action, and application as natural food preservative. Pesticide Biochemistry and Physiology 184: 105066. https://doi.org/10.1016/j.pestbp.2022.105066

Das S, Kumar Singh V, Kumar Dwivedy A, Kumar Chaudhari A, Deepika D, Kishore Dubey N (2021) Nanostructured *Pimpinella anisum* essential oil as novel green food preservative against fungal infestation, aflatoxin B1 contamination and deterioration of nutritional qualities. Food Chemistry 344: 128574. https://doi.org/10.1016/j.foodchem.2020.128574

Divya K, Smitha V, Jisha MS (2018) Antifungal, antioxidant and cytotoxic activities of chitosan nanoparticles and its use as an edible coating on vegetables. International Journal of Biological Macromolecules 114: 572–577. https://doi.org/10.1016/j.ijbiomac.2018.03.130

Divya K, Thampi M, Vijayan S, Varghese S, Jisha MS (2020) Induction of defence response in *Oryza sativa* L. against *Rhizoctonia solani* (Kuhn) by chitosan nanoparticles. Microbial Pathogenesis 149: 104525. https://doi.org/10.1016/j.micpath.2020.104525

Divya K, Vijayan S, George TK, Jisha MS (2017) Antimicrobial properties of chitosan nanoparticles: Mode of action and factors affecting activity. Fibers and Polymers 18(2): 221–230. https://doi.org/10.1007/s12221-017-6690-1

Dmour I, Taha MO (2018) Natural and semisynthetic polymers in pharmaceutical nanotechnology. In: Editor: Grumezescu (Ed.) Organic Materials as Smart Nanocarriers for Drug Delivery. William Andrew Publishing. https://doi.org/10.1016/B978-0-12-813663-8.00002-6

Dorjee L, Gogoi R, Kamil D, Kumar R, Mondal TK, Pattanayak S, Gurung B (2023) Essential oil-grafted copper nanoparticles as a potential next-generation fungicide for holistic disease management in maize. Frontiers in Microbiology 14: 1204512. https://doi.org/10.3389/fmicb.2023.1204512

Dwivedy AK, Singh VK, Prakash B, Dubey NK (2018) Nanoencapsulated *Illicium verum* Hook. f. essential oil as an effective novel plant-based preservative against aflatoxin B1 production and free radical generation. Food and Chemical Toxicology 111: 102–113. https://doi.org/10.1016/j.fct.2017.11.007

El-Aziz ARMA, Al-Othman MR, Mahmoud MA, Shehata SM, Abdelazim NS (2018) Chitosan nanoparticles as a carrier for *Mentha longifolia* extract: synthesis, characterization and antifungal activity. Current Science 114(10): 2116–2122. https://doi.org/10.18520/cs/v114/i10/2116-2122

El-Mohamedy RSR, Abd El-Aziz ME, Kamel S (2019) Antifungal activity of chitosan nanoparticles against some plant pathogenic fungi *in vitro*. Agricultural Engineering International: CIGR Journal 21(4): 201–209. https://cigrjournal.org/index.php/Ejounral/article/view/5425/3209

El-Morsy EM, Elmalahy YS, Mousa MMA (2023) Biocontrol of *Fusarium equiseti* using chitosan nanoparticles combined with *Trichoderma longibrachiatum* and *Penicillium polonicum*. Fungal Biology and Biotechnology 10(1): 5. https://doi.org/10.1186/s40694-023-00151-4

El-Naggar NE, Saber WIA, Zweil AM, Bashir SI (2022) An innovative green synthesis approach of chitosan nanoparticles and their inhibitory activity against phytopathogenic *Botrytis cinerea* on strawberry leaves. Scientific Reports 12(1): 3515. https://doi.org/10.1038/s41598-022-07073-y

Elshaer EE, Elwakil BH, Eskandrani A, Elshewemi SS, Olama ZA (2022) Novel clotrimazole and *Vitis vinifera* loaded chitosan nanoparticles: Antifungal and wound healing efficiencies. Saudi Journal of Biological Sciences 29(3): 1832–1841. https://doi.org/10.1016/j.sjbs.2021.10.041

Fakirov S (2015) Composite materials-is the use of proper definitions important? Materials Today 18(10): 528–529. https://doi.org/10.1016/j.mattod.2015.10.001

Gordienko MG, Palchikova VV, Kalenov SV, Belov AA, Lyasnikova VN, Poberezhniy DY, Chibisova AV, Sorokin VV, Skladnev DA (2019) Antimicrobial activity of silver salt and silver nanoparticles in different forms against microorganisms of different taxonomic groups. Journal of Hazardous Materials 378: 120754. https://doi.org/10.1016/j.jhazmat.2019.120754

Haris M, Hussain T, Mohamed HI, Khan A, Ansari MS, Tauseef A, Khan AA, Akhtar N (2023) Nanotechnology–A new frontier of nano-farming in agricultural and food production and its development. Science of The Total Environment 857: 159639. https://doi.org/10.1016/j.scitotenv.2022.159639

Hasheminejad N, Khodaiyan F, Safari M (2019) Improving the antifungal activity of clove essential oil encapsulated by chitosan nanoparticles. Food Chemistry 275: 113–122. https://doi.org/10.1016/j.foodchem.2018.09.085

Hashim AF, Youssef K, Abd-Elsalam KA (2019) Ecofriendly nanomaterials for controlling gray mold of table grapes and maintaining postharvest quality. European Journal of Plant Pathology 154: 377–388. https://doi.org/10.1007/s10658-018-01662-2

Hassan AA, Oraby NH, El-mesalamy MM, Sayed-ElAhl RMH (2022) Effect of Hybrid Nanomaterial of Copper-Chitosan against Aflatoxigenic Fungi in Poultry Feed. Journal of World's Poultry Research 12(3): 157–164. https://doi.org/10.36380/jwpr.2022.18

Hernández-López G, Ventura-Aguilar RI, Correa-Pacheco ZN, Bautista-Baños S, Barrera-Necha LL (2020) Nanostructured chitosan edible coating loaded with α-pinene for the preservation of the postharvest quality of *Capsicum annuum* L. and *Alternaria alternata* control. International Journal of Biological Macromolecules 165: 1881–1888. https://doi.org/10.1016/j.ijbiomac.2020.10.094

Hernández-Téllez CN, Rodríguez-Córdova FJ, Rosas-Burgos EC, Cortez-Rocha MO, Burgos-Hernández A, Lizardi-Mendoza J, Torres-Arreola W, Martínez-Higuera A, Plascencia-Jatomea M (2017) Activity of chitosan–lysozyme nanoparticles on the growth, membrane integrity, and β-1, 3-glucanase production by *Aspergillus parasiticus*. 3 Biotech 7(5): 279. https://doi.org/10.1007/s13205-017-0913-4

Hesami G, Darvishi S, Zarei M, Hadidi M (2021) Fabrication of chitosan nanoparticles incorporated with *Pistacia atlantica* subsp. kurdica hulls' essential oil as a potential antifungal preservative against strawberry grey mould. International Journal of Food Science & Technology 56(9): 4215–4223. https://doi.org/10.1111/ijfs.15110

Hoang NC, Nguyen CM, Nguyen VH, Giang DH, Nguyen VH, Pham VN (2022) Antifungal activity of squid pen chitosan nanoparticles against three fungal pathogens in various citrus fruits *in vitro* and *in vivo*. Coatings 12(2): 235. https://doi.org/10.3390/coatings12020235

Hsissou R, Seghiri R, Benzekri Z, Hilali M, Rafik M, Elharfi A (2021) Polymer composite materials: A comprehensive review. Composite Structures 262: 113640. https://doi.org/10.1016/j.compstruct.2021.113640

Istúriz-Zapata MA, Correa-Pacheco ZN, Bautista-Baños S, Acosta-Rodríguez JL, Hernández-López M, Barrera-Necha LL (2022) Efficacy of extracts of mango residues loaded in chitosan nanoparticles and their nanocoatings on *in vitro* and *in vivo* postharvest fungal. Journal of Phytopathology 170(10): 661–674. https://doi.org/10.1111/jph.13130

Izadi M, Jorf SAM, Nikkhah M, Moradi S (2021) Antifungal activity of hydrocolloid nano encapsulated *Carum copticum* essential oil and *Peganum harmala* extract on the pathogenic fungi *Alternaria alternata*. Physiological and Molecular Plant Pathology 116: 101714.

Jakovljević V, Đorđević N, Veljković B, Dolićanin Z (2020) Biochemical responses of pure and mixed fungal cultures isolated from waste water to the presence of sodium tripoliphosphates. Acta Scientifica Balcanica 1(1): 19–28.

Jakovljević V, Milićević J, Stojanović J, Solujić S, Vrvić M (2014) The influence of detergent and its components on metabolism of *Fusarium oxysporum* in submerged fermentation. Hemijska Industrija 68(4): 465. https://doi.org/10.2298/HEMIND130620071J

Jonassen H, Kjøniksen AL, Hiorth M (2012) Stability of chitosan nanoparticles cross-linked with tripolyphosphate. Biomacromolecules 13(11): 3747–3756. https://doi.org/10.1021/bm301207a

Jose A, Anitha Sasidharan S, Chacko C, Mukkumkal Jacob D, Edayileveettil Krishnankutty R (2022) Activity of Clove Oil and Chitosan Nanoparticles Incorporated PVA Nanocomposite Against *Pythium aphanidermatum*. Applied Biochemistry and Biotechnology 194: 1442–1457. https://doi.org/10.1007/s12010-021-03709-3

Karami-Osboo R, Mahboubifar M, Mirabolfathy M, Hosseinian L, Reza Jassbi A (2023) Encapsulated *Zataria multiflora's* essential oil inhibited the growth of *Aspergillus flavus* and reduced aflatoxins levels in contaminated pistachio nut. Biocatalysis and Agricultural Biotechnology 51: 102796. https://doi.org/10.1016/j.bcab.2023.102796

Karamchandani BM, Maurya PA, Dalvi SG, Waghmode S, Sharma D, Rahman PK, Ghormade V, Satpute SK (2022) Synergistic activity of rhamnolipid biosurfactant and nanoparticles synthesized using fungal origin chitosan against phytopathogens. Frontiers in Bioengineering and Biotechnology 10: 917105. https://doi.org/10.3389/fbioe.2022.917105

Kalagatur NK, Nirmal Ghosh OS, Sundararaj N, Mudili V (2018) Antifungal activity of chitosan nanoparticles encapsulated with *Cymbopogon martinii* essential oil on plant pathogenic fungi *Fusarium graminearum*. Frontiers in Pharmacology 9: 356156. https://doi.org/10.3389/fphar.2018.00610

Kheiri A, Jorf SM, Malihipour A, Saremi H, Nikkhah M (2016) Application of chitosan and chitosan nanoparticles for the control of Fusarium head blight of wheat (*Fusarium graminearum*) *in vitro* and greenhouse. International Journal of Biological Macromolecules 93: 1261–1272. https://doi.org/10.1016/j.ijbiomac.2016.09.072

Kheiri A, Jorf SM, Malihipour A, Saremi H, Nikkhah M (2017) Synthesis and characterization of chitosan nanoparticles and their effect on Fusarium head blight and oxidative activity in wheat. International Journal of Biological Macromolecules 102: 526–538. https://doi.org/10.1016/j.ijbiomac.2017.04.034

Knabel S, Walker H, Harman P (1991) Inhibition of *Aspergillus flavus* and selected gram-positive bacteria by chelation of essential metal cations by polyphosphates. Journal of Food Protection 54: 360–365. https://doi.org/10.4315/0362-028X-54.5.360

Koukaras EN, Papadimitriou SA, Bikiaris DN, Froudakis, GE (2012) Insight on the formation of chitosan nanoparticles through ionotropic gelation with tripolyphosphate. Molecular Pharmaceutics 9(10): 2856–2862. https://doi.org/10.1021/mp300162j

Kumar A, Gupta V, Singh PP, Kujur A, Prakash B (2020) Fabrication of volatile compounds loaded-chitosan biopolymer nanoparticles: Optimization, characterization and assessment against *Aspergillus flavus* and aflatoxin B1 contamination. International Journal of Biological Macromolecules 165: 1507–1518. https://doi.org/10.1016/j.ijbiomac.2020.09.257

Kumar A, Kujur A, Singh PP, Prakash B (2019) Nanoencapsulated plant-based bioactive formulation against food-borne molds and aflatoxin B1 contamination: Preparation, characterization and stability evaluation in the food system. Food Chemistry 287: 139–150. https://doi.org/10.1016/j.foodchem.2019.02.045

Kumar R, Poonia AK, Duhan JS (2022a) Synthesis, characterization and antimicrobial potential of mancozeb loaded chitosan nanoparticles against *Fusarium pallidoroseum*. Annals of Applied Biology 38: 138–144. https://www.cabidigitallibrary.org/doi/full/10.5555/20220516771

Kumar A, Singh PP, Kumar M, Prakash B (2022b) Nanoencapsulated plant-based antifungal formulation against the *Aspergillus flavus* and aflatoxin B1 contamination: Unraveling the biochemical and molecular mechanism of action. International Journal of Food Microbiology 372: 109681. https://doi.org/10.1016/j.ijfoodmicro.2022.109681

Lang C, Mission EG, Fuaad AAHA, Shaalan M (2021) Nanoparticle tools to improve and advance precision practices in the Agrifoods Sector towards sustainability-A review. Journal of Cleaner Production 293: 126063. https://doi.org/10.1016/j.jclepro.2021.126063

Lipşa FD, Ursu EL, Gafencu AM, Florea MA, Cazacu A (2021) Assessment of antifungal activity of gold-chitosan and carbon nanoparticles against *Rhizoctonia solani* Kühn. Scientific Papers. Series A. Agronomy 64(2): 249–254. https://agronomyjournal.usamv.ro/pdf/2021/issue_2/Art37.pdf

Lipşa FD, Ursu EL, Ursu C, Ulea E, Cazacu A (2020) Evaluation of the antifungal activity of gold–chitosan and carbon nanoparticles on *Fusarium oxysporum*. Agronomy 10(8): 1143. https://doi.org/10.3390/agronomy10081143

López-Meneses AK, Plascencia-Jatomea M, Lizardi-Mendoza J, Fernández-Quiroz D, Rodríguez-Félix F, Mouriño-Pérez RR, Cortez-Rocha MO (2018) *Schinus molle* L. essential oil-loaded chitosan nanoparticles: Preparation, characterization, antifungal and anti-aflatoxigenic properties. Lebensmittel-Wissenschaft & Technologie 96: 597–603. https://doi.org/10.1016/j.lwt.2018.06.013

Luque-Alcaraz AG, Cortez-Rocha MO, Velázquez-Contreras CA, Acosta-Silva AL, Santacruz-Ortega HC, Burgos-Hernández A, Argüelles-Monal WM, Plascencia-Jatomea M (2016) Enhanced antifungal effect of chitosan/pepper tree (*Schinus molle*) essential oil bionanocomposites on the viability of *Aspergillus parasiticus* spores. Journal of Nanomaterials 2016: 6060137. https://doi.org/10.1155/2016/6060137

Makara A, Smol M, Kulczycka J, Kowalski Z (2016) Technological, environmental and economic assessment of sodium tripolyphosphate production – a case study. Journal of Cleaner Production 133: 243–251. https://doi.org/10.1016/j.jclepro.2016.05.096

Malik S, Muhammad K, Waheed Y (2023) Nanotechnology: A revolution in modern industry. Molecules 28(2): 661. https://doi.org/10.3390/molecules28020661

Maluin FN, Hussein MZ, Yusof NA, Fakurazi S, Idris AS, Hilmi NHZ, Daim LDJ (2020) Phytotoxicity of chitosan-based agronanofungicides in the vegetative growth of oil palm seedling. PLOS ONE 15(4): e0231315. https://doi.org/10.1371/journal.pone.0231315

Manikandan A, Sathiyabama M (2016) Preparation of chitosan nanoparticles and its effect on detached rice leaves infected with *Pyricularia grisea*. International Journal of Biological Macromolecules 84: 58–61. https://doi.org/10.1016/j.ijbiomac.2015.11.083

Matei PM, Iacomi BM, Martín-Gil J, Pérez-Lebeña E, Ramos-Sánchez MC, Barrio-Arredondo MT, Martín-Ramos P (2018) *In vitro* antifungal activity of composites of AgNPs and polyphenol inclusion compounds against *Fusarium culmorum* in different dispersion media. Agronomy 8(11): 239. https://doi.org/10.3390/agronomy8110239

Mazzotta E, Muzzalupo R, Chiappetta A, Muzzalupo I (2022) Control of the Verticillium Wilt on tomato plants by means of olive leaf extracts loaded on chitosan nanoparticles. Microorganisms 10(1): 136. https://doi.org/10.3390/microorganisms10010136

Melo NFCB, de Lima MAB, Stamford TLM, Galembeck A, Flores MA, de Campos Takaki GM, da Costa Medeiros JA, Stamford-Arnaud TM, Montenegro-Stamford TC (2020) *In vivo* and *in vitro* antifungal effect of fungal chitosan nanocomposite edible coating against strawberry phytopathogenic fungi. International Journal of Food Science & Technology 55(11): 3381–3391. https://doi.org/10.1111/ijfs.14669

Mohammadi A, Hashemi M, Hosseini SM (2015) Nanoencapsulation of *Zataria multiflora* essential oil preparation and characterization with enhanced antifungal activity for controlling *Botrytis cinerea*, the causal agent of gray mould disease. Innovative Food Science & Emerging Technologies 28: 73–80. https://doi.org/10.1016/j.ifset.2014.12.011

Mondéjar-López M, Rubio-Moraga A, López-Jimenez AJ, García-Martínez JC, Ahrazem O, Gómez-Gómez L, Niza E (2022) Chitosan nanoparticles loaded with garlic essential oil: A new alternative to tebuconazole as seed dressing agent. Carbohydrate Polymers 277: 118815. https://doi.org/10.1016/j.carbpol.2021.118815

Mumtaz T, Ahmed N, ul Hassan N, Badshah M, Khan S (2022) Voriconazole nanoparticles-based film forming spray: An efficient approach for potential treatment of topical fungal infections. Journal of Drug Delivery Science and Technology 70: 102973. https://doi.org/10.1016/j.jddst.2021.102973

Muzzalupo I, Badolati G, Chiappetta A, Picci N, Muzzalupo R (2020) *In vitro* antifungal activity of olive (*Olea europaea*) leaf extracts loaded in chitosan nanoparticles. Frontiers in Bioengineering and Biotechnology 8: 151. https://doi.org/10.3389/fbioe.2020.00151

Nasiri-Jahrodi A, Shams-Ghahfarokhi M, Razzaghi-Abyaneh M (2022) Effects of eugenol-loaded chitosan biopolymer nanoparticles on CYP51A and CYP51B expression in *Aspergillus fumigatus*. Infection Epidemiology and Microbiology 8(1): 17–26. https://doi.org/10.52547/iem.8.1.17

Ouzzani M, Hammady H, Fedorowicz Z, Elmagarmid A (2016) Rayyan — a web and mobile app for systematic reviews. Systematic Reviews 5: 210. https://doi.org/10.1186/s13643-016-0384-4

OH J, Chun SC, Chandrasekaran M (2019) Preparation and *in vitro* characterization of chitosan nanoparticles and their broad-spectrum antifungal action compared to antibacterial activities against phytopathogens of tomato. Agronomy 9(1): 21. https://doi.org/10.3390/agronomy9010021

Palmeira de Oliveira R, Palmeira de Oliveira A, Gaspar C, Silvestre S, Martinez de Oliveira J, Amaral MH, Breitenfeld L (2011) Sodium Tripolyphosphate: An excipient with intrinsic *in vitro* anti-Candida activity. International Journal of Pharmaceutics 421(1): 130–134. https://doi.org/10.1016/j.ijpharm.2011.09.030

Parthasarathy R, Jayabaskaran C, Manikandan A, Anusuya S (2023) Synthesis of nickel-chitosan nanoparticles for controlling blast diseases in asian rice. Applied Biochemistry and Biotechnology 195(3): 2134–2148. https://doi.org/10.1007/s12010-022-04198-8

Pham TT, Nguyen TH, Thi TV, Nguyen TT, Le TD, Vo DMH, Nguyen DH, Nguyen CK, Nguyen DC, Nguyen TT, Bach LG (2019) Investigation of chitosan nanoparticles loaded with protocatechuic acid (PCA) for the resistance of pyricularia oryzae fungus against rice blast. Polymers 11(1): 177. https://doi.org/10.3390/polym11010177

Rampino A, Borgogna M, Blasi P, Bellich B, Cesàro A (2013) Chitosan nanoparticles: Preparation, size evolution and stability. International Journal of Pharmaceutics 455(1–2): 219–228. https://doi.org/10.1016/j.ijpharm.2013.07.034

Saharan V, Mehrotra A, Khatik R, Rawal P, Sharma SS, Pal A (2013) Synthesis of chitosan based nanoparticles and their *in vitro* evaluation against phytopathogenic fungi. International Journal of Biological Macromolecules 62: 677–683. https://doi.org/10.1016/j.ijbiomac.2013.10.012

Saharan V, Sharma G, Yadav M, Choudhary MK, Sharma SS, Pal A, Raliya R, Biswas, P (2015) Synthesis and *in vitro* antifungal efficacy of Cu–chitosan nanoparticles against pathogenic fungi of tomato. International Journal of Biological Macromolecules 75: 346–353. https://doi.org/10.1016/j.ijbiomac.2015.01.027

Salem MF, Abd-Elraoof WA, Tayel AA, Alzuaibr FM, Abonama OM (2022) Antifungal application of biosynthesized selenium nanoparticles with pomegranate peels and nanochitosan as edible coatings for citrus green mold protection. Journal of Nanobiotechnology 20(1): 182. https://doi.org/10.1186/s12951-022-01393-x

Sarkar A, Chakraborty N, Acharya K (2022) Chitosan nanoparticles mitigate Alternaria leaf spot disease of chilli in nitric oxide dependent way. Plant Physiology and Biochemistry 180: 64–73. https://doi.org/10.1016/j.plaphy.2022.03.038

Sathiyabama M, Gandhi M, Indhumathi M (2022) Suppression of dry root rot disease caused by *Rhizoctonia bataticola* (Taub.) Butler in chickpea plants by application of thiamine loaded chitosan nanoparticles. Microbial Pathogenesis 173: 105893. https://doi.org/10.1016/j.micpath.2022.105893

Sathiyabama M, Muthukumar S (2020) Chitosan guar nanoparticle preparation and its *in vitro* antimicrobial activity towards phytopathogens of rice. International Journal of Biological Macromolecules 153: 297–304. https://doi.org/10.1016/j.ijbiomac.2020.03.001

Sathiyabama M, Parthasarathy R (2016) Biological preparation of chitosan nanoparticles and its *in vitro* antifungal efficacy against some phytopathogenic fungi. Carbohydrate Polymers 151: 321–325. https://doi.org/10.1016/j.carbpol.2016.05.033

Sen SK, Tripathi R, Mandal P, Choudhuri C (2022) Assessment of antifungal activity of nano-chitosan against mung bean seed borne pathogen *Aspergillus flavus* through solid matrix priming. South African Journal of Botany 150: 372–386. https://doi.org/10.1016/j.sajb.2022.06.016

Singh A, Deepika D, Chaudhari AK, Das S, Singh VK, Dwivedy AK, Shivalingam RK, Dubey NK (2020a) Assessment of preservative potential of *Bunium persicum* (Boiss) essential oil against fungal and aflatoxin contamination of stored masticatories and improvement in efficacy through encapsulation into chitosan nanomatrix. Environmental Science and Pollution Research 27: 27635–27650. https://doi.org/10.1007/s11356-020-08872-4

Singh PP, Kumar A, Prakash B (2020b) Elucidation of antifungal toxicity of *Callistemon lanceolatus* essential oil encapsulated in chitosan nanogel against *Aspergillus flavus* using biochemical and *in-silico* approaches. Food Additives & Contaminants: Part A 37(9): 1520–1530. https://doi.org/10.1080/19440049.2020.1775310

Stojanović J, Jakovljević V, Matović I, Gajović O, Mijušković Z, Nedeljković T (2011) Influence of detergent on metabolic activity of fungi *Aspergillus niger*. Natural Science 3(6): 466–470. https://doi.org/10.4236/ns.2011.36064

Stojanović J, Jakovljević V, Matović I, Mijušković Z, Nedeljković T (2010) The influence of detergents, sodium tripoly phosphates and ethoxyled oleyl-cetyl alcohol on metabolism of the fungi *Penicillium verrucosum* Peyronel. Acta veterinaria 60(1): 67–77. https://doi.org/10.2298/AVB1001067S

Tiwari S, Upadhyay N, Singh BK, Singh VK, Dubey NK (2022) Facile fabrication of nanoformulated *cinnamomum glaucescens* essential oil as a novel green strategy to boost potency against food borne fungi, aflatoxin synthesis, and lipid oxidation. Food and Bioprocess Technology 15: 319–337. https://doi.org/10.1007/s11947-021-02739-3

Wang Y, Li S, Wang X, Xu J, Li T, Zhu J, Yang R, Wang J, Chang M, Wang L (2021) Biochelator assisted phytoremediation for cadmium (Cd) pollution in paddy field. Sustainability 13(21): 12170. https://doi.org/10.3390/su132112170

Wardana AA, Wigati LP, Tanaka F, Tanaka F (2023) Incorporation of co-stabilizer cellulose nanofibers/chitosan nanoparticles into cajuput oil-emulsified chitosan coating film for fruit application. Food Control 148: 109633. https://doi.org/10.1016/j.foodcont.2023.109633

Wu J, Chang J, Liu J, Huang J, Song Z, Xie X, Wei L, Xu J, Huang S, Cheng D, Li Y, Xu H, Zhang Z (2023) Chitosan-based nanopesticides enhanced anti-fungal activity against strawberry anthracnose as "sugar-coated bombs". International Journal of Biological Macromolecules 253: 126947. https://doi.org/10.1016/j.ijbiomac.2023.126947

Xing Y, Wang X, Guo X, Yang P, Yu J, Shui Y, Chen C, Li X, Xu Q, Xu L, Bi X, Liu X (2021) Comparison of antimicrobial activity of chitosan nanoparticles against bacteria and fungi. Coatings 11: 769. https://doi.org/10.3390/coatings11070769

Xiong Y, Feng YX, Chang M, Wang Q, Yin SN, Jian LY, Ren DF (2023) Formulated chitosan-sodium tripolyphosphate nanoparticles for co-encapsulation of ellagic acid and anti-inflammatory peptide: characterization, stability and anti-inflammatory activity. Journal of the Science of Food and Agriculture 103(7): 3447–3456. https://doi.org/10.1002/jsfa.12521

Yadav A, Kujur A, Kumar A, Singh PP, Prakash B, Dubey NK (2019) Assessing the preservative efficacy of nanoencapsulated mace essential oil against food borne molds, aflatoxin B1 contamination, and free radical generation. Lebensmittel-Wissenschaft & Technologie 108: 429–436. https://doi.org/10.1016/j.lwt.2019.03.075

Yilmaz MT, Yilmaz A, Akman PK, Bozkurt F, Dertli E, Basahel A, Al-Sasi B, Taylan O, Sagdic O (2019) Electrospraying method for fabrication of essential oil loaded-chitosan nanoparticle delivery systems characterized by molecular, thermal, morphological and antifungal properties. Innovative Food Science & Emerging Technologies 52: 166–178. https://doi.org/10.1016/j.ifset.2018.12.005

Youssef K, de Oliveira AG, Tischer CA, Hussain I, Roberto SR (2019) Synergistic effect of a novel chitosan/silica nanocomposites-based formulation against gray mold of table grapes and its possible mode of action. International Journal of Biological Macromolecules 141: 247–258. https://doi.org/10.1016/j.ijbiomac.2019.08.249

Zielińska A, Carreiró F, Oliveira AM, Neves A, Pires B, Venkatesh DN, Durazzo A, Lucarini M, Eder P, Silva AM, Santini A, Souto EB (2020) Polymeric nanoparticles: production, characterization, toxicology and ecotoxicology. Molecules 25(16): 3731. https://doi.org/10.3390/molecules25163731

Zweben C (2024) Encyclopedia of Condensed Matter Physics (Second Edition). Newtown Square, PA, United States 5: 333–349. https://doi.org/10.1016/B978-0-323-90800-9.00055-X

Supplementary material

Supplementary material 1
Research results from various databases (zip. archive)
Link: https://doi.org/10.3897/ejfa.2024.119832.suppl1